

**TEST REPORT**

Report No: 09722-26R
Receiving Date: 08 April 2026
Issue Date: 10 April 2026
Revision Date: 18 April 2026

Buyer : Self Reference
Agent : /
Label : /
Content(Claimed) : 100%Cotton

Weight : /
Previous Report No : /
Design : /
Fabric : Canvas
Construction : 7/2x7/2 PANTHEON

Color : Green

Style : /
Style No : /
PO No : /
Vender Ref # : /
Description : Fabric Swatch
Care instruction : /

Program : /
Country of origin : /
Destination : /
Size : /
Season :
Department : /
Protocol : /
End Use : /



For and on behalf of
TEXTILE TESTING INTERNATIONAL

Ali Ashraf
AVP Softlines



Report No: 09722-26R

Test Conducted**Requirements****1. Tearing strength - Tongue (Single Rip)**

ASTM D2261-2017

Option 1: Average of 5 Highest Peaks

Warp	8.99 lbs
Weft	7.2 lbs

2. Breaking strength & elongation - Grab Method

ASTM D5034:2021

Sample size: 6x4 Inch

Gauge length: 75 mm

Machine speed: 300 mm/min

	<u>Strength</u>
Warp	222.3 lbs
Weft	133.7 lbs

3. Color fastness to crocking

AATCC 8-2022

Dry (Color Stain)	4.0
Wet (Color Stain)	3.0

4. Color fastness to laundering: Accelerated

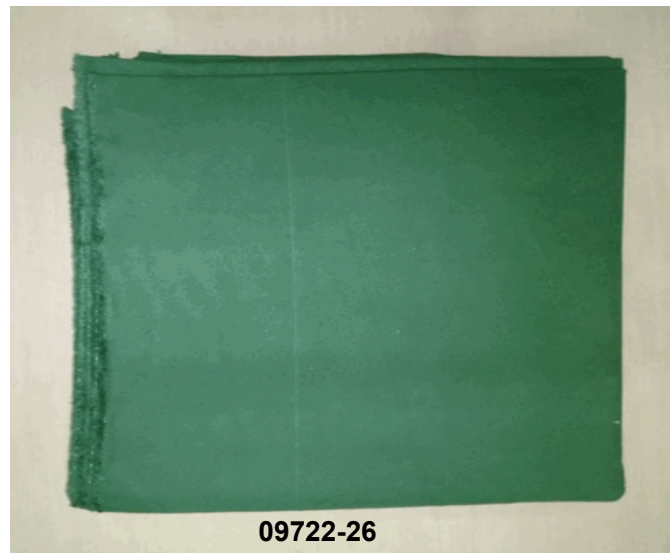
AATCC 61-2A:2020

(45 minutes mechanical wash in Launder-O-meter at 49±2°C, 0.15% AATCC 1993 WOB detergent solution with 50 steel balls)

Color Change	4.5
Staining On:	-
Acetate	4.0
Cotton	3.5
Nylon 6.6	4.0
Polyester	4.5
Acrylic	4.5
Wool	4.0

**Report No:** 09722-26R**Test Conducted****Requirements****Color Fastness Rating**

- 5 Negligible/No change or staining
- 4 Slightly changed or staining
- 3 Noticeably changed or staining
- 2 Considerably changed or staining
- 1 Much changed or staining

Digital Image of Sample

**** END OF REPORT ****